



中国认可  
国际互认  
检测  
TESTING  
CNAS L3457



江苏中纺联检验技术服务有限公司  
United Testing Services (Jiangsu) Co., Ltd.

## 检测报告

防伪查询网址: [www.fcl-sz.org.cn](http://www.fcl-sz.org.cn)  
防伪码: 2815226256



报告编号: ZFLJ0682088

第 1 页, 共 3 页

### Applicant Information (客户信息)

Applicant Name(委托单位) : Jiashan Hongtai Printing Material Co., Ltd. (嘉善鸿泰喷印材料有限公司)  
Contact person(委托人) : Hu Qian(胡乾)

### Sample Information (样品信息)

Sample Description(样品描述) : One piece of white coating woven fabric (一块白色涂层机织面料)  
Style Name(品名) : 数码气模布  
Sample Quantity(样品数量) : 2m\*1m

- Sample receiving/Test started date (样品受理/检测起始日期) : 2023-03-11
- Report date (报告日期) : 2023-03-14
- The original sample is stuck on the last paper. (送检样品原样粘贴在本报告的末页)

### Test Performed (检验标准)

Judgement according to(评定依据):

GB/T 17591-2006 Flame retardant fabrics B1 grade Decorative fabric  
阻燃织物 B1 级 装饰用织物

- Selected test(s) as requested by applicants. (本实验室根据客户要求完成以下检测内容)

### Pronounce (声明)

The test report cannot be reproduced, except in full. The reproduced report is invalid if the original stamp of testing and inspection is omitted. The following test(s) were completed according to the applicant's requirements and the results shown in this report refer only to sample(s) tested. (检测报告不得部分复制, 全文复制除外, 复制报告未加盖本机构“检验检测专用章”无效。本实验室根据客户要求完成以上检测内容, 检测结果只对来样负责。)

The test results and the conformity judgement of this report do not take the uncertainty of the test results into account. (本报告检测结果及符合性判定不考虑测量结果的不确定度。)

Signed for and on behalf of

United Testing Services (Jiangsu) Co., Ltd.

| Approved by<br>(批准) | Main testing by<br>(主检) | Prepare by<br>(制单) |
|---------------------|-------------------------|--------------------|
| 王榴艳                 | 惠永久                     | 陈嘉颖                |



地址: 江苏省苏州市吴江区盛泽镇西环二路 1018 号 No.1018, West Ring 2nd Road, Shengze, Wujiang District, Suzhou, Jiangsu

邮编/Post code: 215228 电话/Tel: (86 512) 63081315/63081937 传真/Fax: (86 512) 63515226

若对检测报告有异议, 应于收到报告之日起 15 日内向检测单位提出, 逾期不予受理。



中国认可  
国际互认  
检测  
TESTING  
CNAS L3457



江苏中纺联检验技术服务有限公司  
United Testing Services (Jiangsu) Co., Ltd.

## 检测报告

防伪查询网址: www.fcl-sz.org.cn

防伪码: 2815226256



报告编号: ZFLJ0682088

第 2 页, 共 3 页

### --- Test Result (测试结果) ---

#### 1. Flammability(燃烧性测试) GB/T 5455-2014 Vertical Method (垂直法)

Testing environment(测试环境) : Humidity conditions A, Temperature: 20.7°C, humidity:60.8%.  
(调湿条件 A, 试验温度: 20.7°C, 湿度: 60.8%。)

Ignition source(火源) : Butane(丁烷)

Flame application time(点火时间) :12s

|                                                               | Warp(经向)     |     |      |     |     | Weft(纬向)     |     |     |     |     | Requirements(要求) |
|---------------------------------------------------------------|--------------|-----|------|-----|-----|--------------|-----|-----|-----|-----|------------------|
|                                                               | 1            | 2   | 3    | 4   | 5   | 1            | 2   | 3   | 4   | 5   |                  |
| Afterflame time*<br>(续燃时间) (s)                                | 1.03         | 0.0 | 3.15 | 0.0 | 0.0 | 0.0          | 0.0 | 0.0 | 0.0 | 0.0 | --               |
| Average of afterflame time<br>平均续燃时间 (s)                      | /            |     |      |     |     | 0.0          |     |     |     |     | ≤5               |
| Afterglow time<br>(阴燃时间) (s)                                  | 0.0          | 0.0 | 0.0  | 0.0 | 0.0 | 0.0          | 0.0 | 0.0 | 0.0 | 0.0 | --               |
| Average of Afterglow time<br>平均阴燃时间 (s)                       | 0.0          |     |      |     |     | 0.0          |     |     |     |     | ≤5               |
| Damaged length<br>(损毁长度) (mm)                                 | 114          | 117 | 118  | 125 | 120 | 115          | 117 | 108 | 122 | 112 | --               |
| Average of Damaged<br>length<br>(平均损毁长度) (mm)                 | 119          |     |      |     |     | 115          |     |     |     |     | ≤150             |
| Sample characteristic after<br>burning(试样燃烧后特征)               | Melting (熔融) |     |      |     |     | Melting (熔融) |     |     |     |     | --               |
| Whether there was any<br>dripping when burning<br>(燃烧时是否有滴落物) | No(否)        |     |      |     |     | No(否)        |     |     |     |     | --               |
| Was absorbent cotton<br>burning or smoldering<br>(脱脂棉是否燃烧或阴燃) | No(否)        |     |      |     |     | No(否)        |     |     |     |     | --               |
| Conclusion(结论)                                                |              |     |      |     |     |              |     |     |     |     | Pass(合格)         |

Remark(备注): “\*”Report the individual value of 5 specimens due to uneven results obtained in warp direction.  
 (“\*”经向结果不均, 报告 5 个试样的测试结果)

地址: 江苏省苏州市吴江区盛泽镇西环二路 1018 号 No.1018, West Ring 2nd Road, Shengze, Wujiang District, Suzhou, Jiangsu

邮编/Post code:215228 电话/Tel:(86 512)63081315/63081937 传真/Fax:(86 512)63515226

若对检测报告有异议, 应于收到报告之日起 15 日内向检测单位提出, 逾期不予受理。





中国认可  
国际互认  
检测  
TESTING  
CNAS L3457



江苏中纺联检验技术服务有限公司  
United Testing Services (Jiangsu) Co., Ltd.

## 检测报告


防伪查询网址: [www.fcl-sz.org.cn](http://www.fcl-sz.org.cn)  
防伪码: 2815226256



报告编号: ZFLJ0682088

第 3 页, 共 3 页

Original (送检样品原样)

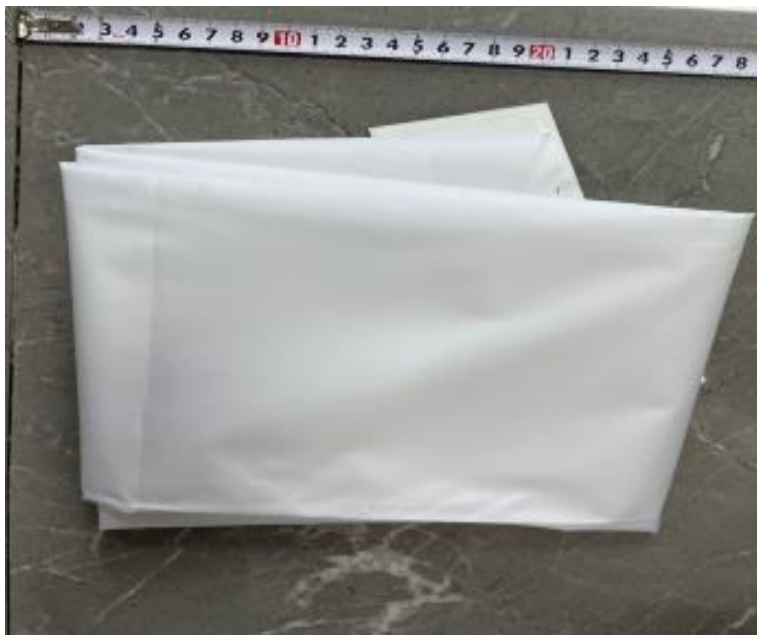

===== End of Report (检测报告结束) =====

地址: 江苏省苏州市吴江区盛泽镇西环二路 1018 号 No.1018, West Ring 2nd Road, Shengze, Wujiang District, Suzhou, Jiangsu

邮编/Post code: 215228 电话/Tel: (86 512) 63081315/63081937 传真/Fax: (86 512) 63515226

若对检测报告有异议, 应于收到报告之日起 15 日内向检测单位提出, 逾期不予受理。

